

"Original contains color  
plates: All DTIC reproduct-  
ions will be in black and  
white"

ARL-MAT-TM-404

AR-006-602

AD-A243 000



DTIC  
ELECTE  
DEC 6 1991  
S C D

DEPARTMENT OF DEFENCE  
DEFENCE SCIENCE AND TECHNOLOGY ORGANISATION  
AERONAUTICAL RESEARCH LABORATORY  
MELBOURNE, VICTORIA

Aircraft Materials Technical Memorandum 404

METALLOGRAPHY OF ALUMINIDE COATINGS

by

P. ROHAN

91-17081



Approved for public release

© COMMONWEALTH OF AUSTRALIA 1991

MAY 1991

01 12 4 077

05

This work is copyright. Apart from any fair dealing for the purpose of study, research, criticism or review, as permitted under the Copyright Act, no part may be reproduced by any process without written permission. Copyright is the responsibility of the Director Publishing and Marketing, AGPS. Enquiries should be directed to the Manager, AGPS Press, Australian Government Publishing Service, GPO Box 84, CANBERRA ACT 2601.

**DEPARTMENT OF DEFENCE  
DEFENCE SCIENCE AND TECHNOLOGY ORGANISATION  
AERONAUTICAL RESEARCH LABORATORY**

Aircraft Materials Technical Memorandum 404

**METALLOGRAPHY OF ALUMINIDE COATINGS**

by

P. ROHAN

**SUMMARY**

*Metallographic techniques have been established for the examination of gas turbine blades and their protective coatings. Particular attention was given to edge retention of specimens during polishing and to etchant selection to allow microstructural evaluation of major phases. Edge retention was achieved firstly by depositing a nickel plate over the specimen (by electroless deposition) and secondly, by minimizing the use of cloth polishing pads. Etchants were then evaluated for phase delineation in polished Allison T-56 turbine blades, (IN738 substrate alloy coated with high-activity nickel aluminide). Characteristics of four most useful etchants are described.*



© COMMONWEALTH OF AUSTRALIA 1991

---

**POSTAL ADDRESS:** Director, Aeronautical Research Laboratory  
506 Lorimer Street, Fishermens Bend 3207  
Victoria Australia

## CONTENTS

	<u>Page No.</u>
1. INTRODUCTION.....	1
2. EDGE RETENTION.....	2
2.1 Nickel Plating.....	2
2.2 Polishing.....	3
3. ETCHANTS.....	4
3.1 Carbide Stain.....	4
4. CONCLUSION.....	5
5. REFERENCES.....	6
APPENDIX.....	7

Accession For	
NTIS Grant	<input checked="" type="checkbox"/>
ERIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	



## **1.0 INTRODUCTION**

The Corrosion Control group at ARL has commenced a programme for evaluating protective coatings for gas turbine blades currently used by the RAAF (work previously performed at MRL). To enable examination and evaluation of metallographic specimens (with particular attention given to surface features), techniques have been developed for sample preparation and microstructural etching. In developing these techniques, Allison T-56 turbine engine blades cast from a nickel-based superalloy (IN 738) and coated with nickel aluminide were sectioned. The nickel aluminide coating applied by a high-activity "pack-cementation" process to the outer surface of the blades, imparts oxidation/corrosion resistance to the substrate superalloy. Metallographic procedures were developed with an aim to minimise edge rounding and highlight the detailed microstructure by selective etching. As the coatings are only between 50 and 100  $\mu\text{m}$  thick and attention needs to be given to oxide/corrosion scales produced on the surface, edge retention is essential.

Nickel-based superalloys are composed of FCC  $\gamma$  - Ni solid solution containing  $\gamma'$  -  $\text{Ni}_3\text{Al}$  precipitation phase, carbides and various other precipitates such as  $\eta$ , (hcp, eg  $\text{Ni}_3\text{Ti}$ ),  $\sigma$ , (tcp, eg CrCo, CrNiMo), etc. (ref. 1). The coating mainly consists of  $\beta$  -  $\text{NiAl}$  and may contain precipitate particles and carbides derived from alloying elements contained in the substrate (ref. 2). Various etchants have been used to reveal these features with the most useful being reported here.

The blades used were rejects from routine maintenance performed by the RAAF on Allison T56 turbo-prop engines (from either the C-130 Hercules or P-3 Orion aircraft) and as such showed various defects and coating conditions.

## **2.0 EDGE RETENTION**

In order to minimise edge rounding during (manual) polishing of specimens, 2 steps were taken:


1. A Ni coating is first plated over the sample.  
(Ni electroplating of specimens was previously used by MRL for related work)
2. SiC paper was used down to 4000# (5µm) to minimise the use of cloth pads (which exacerbate edge rounding).

## **2.1 NICKEL PLATING**

To avoid loss of corrosion products from the outer surface of samples during immersion in plating solutions and due to handling, entire blades were vacuum impregnated with epoxy resin. The viscosity of the epoxy was sufficiently low to allow penetration of the scale and prevent fragmenting during polishing. After impregnation, the excess resin was allowed to run off leaving only a thin film to cure over the surface. The cured epoxy must have high hardness and minimal shrinkage to prevent scale separation from the coating.

400# SiC paper was later used to roughen the cured epoxy surface to allow mechanical 'keying-in' of the plated coating and avoid flaking.

The procedure for the electroless deposition of nickel is given in Table 1. Firstly, the surface to be plated was cleared of contaminants by placing the sample in a beaker of acetone and cleaning ultrasonically. After drying, the sample is placed in the sensitizing-nucleating solution where the following reaction takes place (ref. 3):



ie. palladium chloride is reduced to colloidal Pd metal particles by  $\text{Sn}^{2+}$ , which then forms hydrolysed  $\text{Sn}^{4+}$  which in turn stabilises the Pd colloid.

Before the sample can be plated in the electroless Ni bath, the  $\text{Sn}^{4+}$  ions surrounding the adsorbed Pd must be removed. This 'acceleration' step dissolves the  $\text{Sn}^{4+}$  without affecting the Pd layer.

The electroless Ni bath itself contains essentially,

- a) a Ni salt ( $\text{NiSO}_4 \cdot 6\text{H}_2\text{O}$ ),
- b) a reducing agent (sodium hypophosphite,  $\text{NaH}_2\text{PO}_4 \cdot 6\text{H}_2\text{O}$ );

and results in the following reaction:



Sodium acetate ( $\text{NaC}_2\text{H}_3\text{O}_2$ ) is added to increase the deposition rate and buffer the solution, while the other additive, lead acetate ( $\text{Pb}(\text{C}_2\text{H}_3\text{O}_2)_2 \cdot 2\text{H}_2\text{O}$ ) stabilises the bath to prevent catalytic decomposition (ref. 3).

An alternative to electroless deposition is to sputter a conducting film over the epoxy and then electroplate a Ni coating using the low stress sulphamate bath (ref. 1); this would be useful for a small number of specimens as the electroless bath has a short life (the procedure for electroplating is given in appendix 1).

After plating, the specimens are mounted in epoxy resin for polishing (see figs. 1 & 2).

## **2.2 POLISHING**

When the mounting epoxy had cured, the samples were abraded with SiC paper ranging from 220# to 4000# using ethanol for cleaning and lubrication. Interchangeable SiC paper discs were used which clipped onto a brass polishing wheel. Care was taken to retain the brittle scale during polishing which, besides being lost, would scratch the specimen on breaking free. After 4000#, final polishing was carried out using 1 $\mu\text{m}$  diamond paste on a felt pad.

Edge rounding still occurs to some degree; however, for better results, automatic polishing would be required.

### **3.0 ETCHANTS**

Many etchants have been tried, the most useful are those listed in Table 2. Relevant figures (with detailed captions) and microstructures are referenced in the table.

In Table 2, it may appear that the lactic acid etch (etchant (1)) and the iron chloride etch (etchant (2)) perform similarly; however they are quite different. Etchant (1) was used for microstructural observation of both substrate and coating to good effect. Etchant (2) was too severe on the aluminide coating for optical microscopy and was more useful as a macroetchant, as it colour contrasted the dendritic structure of the grains (fig. 8). As a consequence of its preferential attack of Al rich phases, it has been used to strip the coating from a blade leaving the skeleton of the scale, coating grain boundaries and the precipitation region of the substrate (fig. 14).

The electrolytic etchants can be used for phase extraction; ie. electrolyte (1), when used for longer periods, can be used to dissolve the substrate leaving  $\gamma'$  precipitates (fig. 9) and electrolyte (2) can be used for carbide extraction (fig. 11), as little dissolution of these phases occur, compared to the surrounding material.

### **3.1 CARBIDE STAIN**

Figures 15 and 16 show examples of the effect obtained using the carbide stain. Two different superalloys are shown; in figure 15, IN 738 was stained to reveal the blocky matrix carbides of  $M_6C$  type; while in figure 16, the matrix carbides are  $M_{23}C_6$  in René 80H.

A chain of small discrete carbide particles is developed in superalloy grain boundaries during post-forming aging to improve creep rupture life (ref 1). Due to the presence of these carbides in grain boundaries, the carbide stain can also be used to delineate grains on a polished specimen without destructive etching, (fig. 17).



#### **4.0 CONCLUSION**

1. Edge retention of polished turbine blade specimens is essential for examination of the aluminide coating applied to the outer surface. This has been achieved by nickel plating an approximately 30  $\mu\text{m}$  thick layer over the specimen before mounting and polishing.
2. Four etchants have been selected for their ease of use and phase delineation:
  - i. a microetchant (immersion) for coating and substrate.
  - ii. a macroetchant (immersion) for the substrate.
  - iii. an electrolytic microetchant for the substrate and for phase extraction of  $\gamma'$ .
  - iv. an electrolytic microetchant for substrate and coating, and phase extraction of carbides.

In addition, a carbide stain was used to identify carbide phases by colour contrasting.

## **5.0 REFERENCES**

1. ASM, Metals Handbook, 9th edition.
2. G. R. Johnston, P. G. Richards, "High-Temperature Corrosion in Military Gas Turbines: A Metallographic Comparison of ALPAK Aluminide and CAC Aluminide Coatings for First-Stage Turbine Blades in RAAF T-56 Engines". MRL report, MRL-R-817, (1981).
3. F. A. Lowenheim, "Electroplating", McGraw-Hill Pub. (1978).
4. R. Kossowsky, S. Singhal (eds.), "Surface Engineering", Martinus Nijhoff Pub., (1984).
5. ASTM, "Standard Methods For Microetching Of Metals and Alloys". Designation E407, Etchant No. 40.
6. E. Kny, "On The Methodology of Phase Extraction in Ni Based Superalloys", Praktische Metallographie, 13, (1976).
7. P. J. Fink, R. W. Heakel, "Analysis of Microstructural Change due to Cyclic Oxidation in Aluminide-coated Ni-Al, Ni-Cr and Ni-Cr-Al Alloys", High Temperature Coatings, The Metallurgical Society Pub., (1986).

## **APPENDIX 1.**

Instead of the electroless plating procedure, a Ni coating may be applied by electroplating if a conducting film exists on the surface. A conducting film may be applied simply by sputtering techniques; however, of the metals tried, gold performed the best so this was used sparingly.

The electroplating bath that was most satisfactory, by way of solution stability and producing a coating of low stress, was the Sulphamate Bath (ref. 1):

$\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$	0-30g/l
$\text{Ni}(\text{SO}_3 \cdot \text{NH}_2)_2$	260-450g/l
$\text{H}_3\text{BO}_3$	30-45g/l (or to pH)

### **Operating Conditions:**

pH	3 - 5
temp	38-60°C
current density	100 mA/cm <sup>2</sup> (constant current power supply)
time	1 hr.
constant agitation.	

---

**TABLE 1: ELECTROLESS NICKEL PLATING PROCEDURE.**

STEP	ACTION	FORMULA
1	Clean specimen	Acetone & ultrasound.
2	Sensitizing/nucleating (ref. 3)	Stannous chloride 2g/l Palladium chloride 0.2g/l HCl 10ml/l in H <sub>2</sub> O Immerse 1 min 20-40°C.
3	Acceleration (ref. 1)	Dilute HCl Immerse 30 sec 50°C.
4	Plating bath (ref. 4)	Nickel sulphate 25 g/l Sodium acetate 9 g/l Lead acetate 0.001 g/l Sodium hypophosphite 23 g/l Immerse 60 mins. 80°C, pH 4-5.


**TABLE 2: ETCHANTS FOR NICKEL BASED SUPERALLOYS.**

ETCHANT	USE	EFFECT / COMMENTS
<b>1.</b> (ref. 5) 30ml Lactic acid 30ml Acetic acid 20ml HCl 10ml HNO <sub>3</sub>	Immerse 5 sec	Dissolves $\gamma'$ & $\beta$ , leaves $\alpha$ -Cr in coating; good for micro-structure of coating and substrate. (figs. 3 to 5)
<b>2.</b> (ref. 6) 5g FeCl <sub>3</sub> 15ml HCl 60ml Ethanol	Immerse 5 sec	Dissolves $\gamma'$ & $\beta$ ; good macro etch, reveals grain structure of substrate and coating. (figs. 6 to 8)
<b>3.</b> Electrolyte (1) (ref. 5) 1% Citric acid 1% Ammonium-sulphate in H <sub>2</sub> O	1V, 10 sec*	Dissolves substrate leaving $\gamma'$ . (figs. 9 & 10)
<b>4.</b> Electrolyte (2) (ref. 7) 10% HCl 4% Tartaric acid in Methanol	2V, 10 sec*	Dissolves coating & substrate leaving carbides and interdiffusion zone precipitates. (figs. 11 to 13)
Carbide stain (ref. 5): 50/50 Aqueous soln. K <sub>2</sub> MnO <sub>4</sub> and 60% NaOH soln.	Swab 3 sec	Stains carbides according to structure: - M <sub>23</sub> C <sub>6</sub> green-pale blue - M <sub>6</sub> C brown - MC multicoloured. (figs. 15 to 17)


\* For a specimen area of approximately 1.5cm<sup>2</sup> .




**Figure 1:** Edge and corrosion product retention using the Ni plating procedure.

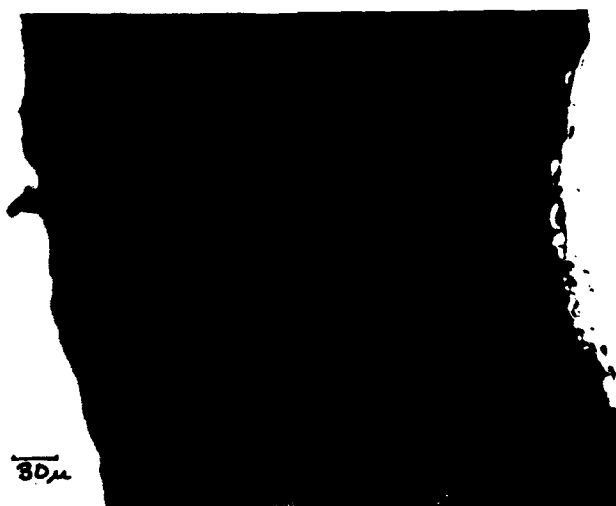


**Figure 2:** Retention of corrosion product produced by static laboratory tests; the bright band on LHS is the blade material, RHS is Ni plate.

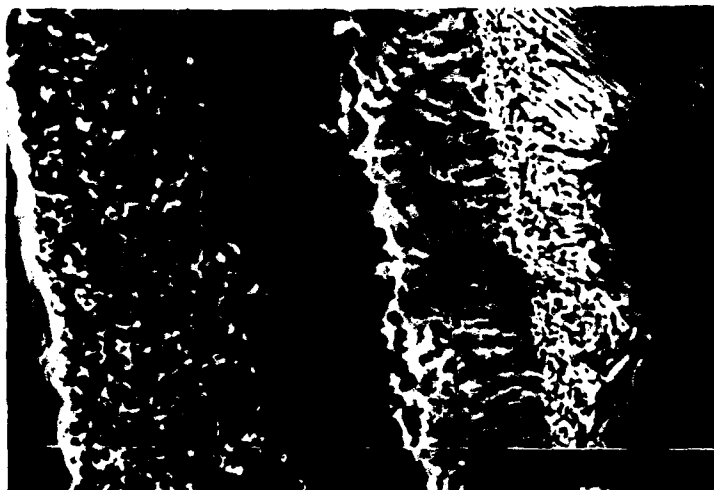

**Figure 3:** SEM micrograph of the effect of etchant (1) on a high activity aluminide coating. On the RHS of the micrograph, the  $\gamma$  matrix contains voids where  $\gamma'$  has been removed. To the left is the interdiffusion zones which are highlighted due to dissolution of  $\gamma'$  (inner) and  $\beta$  (outer) phases which previously surrounded the precipitates. The coating  $\beta$  phase has been dissolved revealing precipitates arising from substrate alloying elements in two distinct bands; a finer precipitate size close to the outer interdiffusion zone, and a coarser precipitate toward the outer edge. Little oxidation of this coating has occurred as there is no indication of  $\gamma'$  formation due to Al depletion, (ref.7).

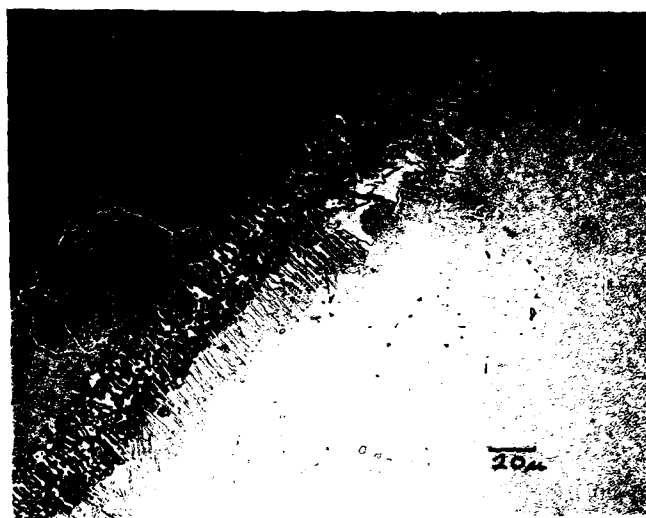

**Figure 4:** Optical micrograph showing the effect of etchant (1) on the substrate and coating. The coating grain structure is revealed (showing less precipitates than fig. 3 due to solutioning during service) and the substrate  $\gamma$ ,  $\gamma'$ , carbides and grain boundaries are clearly seen.

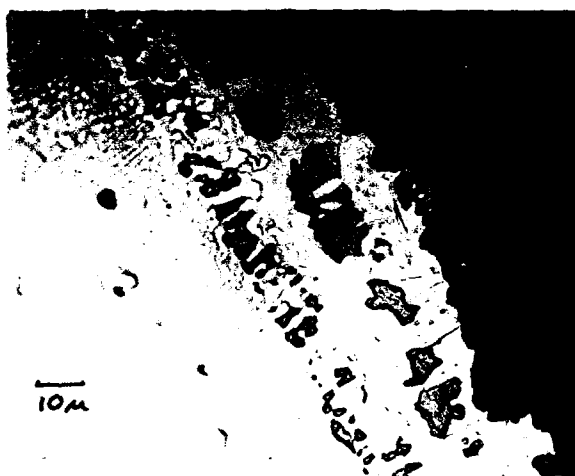

**Figure 5:** Also etchant (1), but here the coating has undergone Al depletion as the  $\beta$  phase exists only as isolated grains in the coating; the rest of the coating is probably  $\gamma'$  phase.






**Figure 6:** SEM micrograph obtained using etchant (2). This etchant has revealed more coating structure for a similar coating area to fig. 4 due to preferential attack on Al rich regions. Because of this, etchant (2) is not as applicable for optical micrographs as etchant (1).




**Figure 7:** A different coating area than in fig. 6 (also etchant (2)) showing greater solutioning of coating precipitates due to longer service exposure. Oxidation is also visible down a coating grain boundary reaching the substrate.

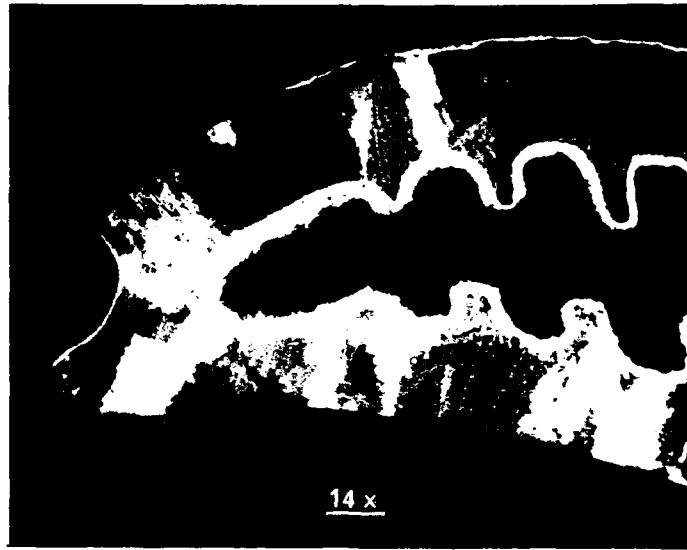

**Figure 8:** Colour contrasting effect of etchant (2) on macrostructure. The dendritic grain structure and corrosion depleted regions are clearly defined (LHS is leading edge).



**Figure 9:** In this micrograph, etchant (3) has been used to isolate  $\gamma'$  in the substrate (LHS). The  $\beta$  phase of the coating is intact and the interdiffusion zone precipitates have dissolved.

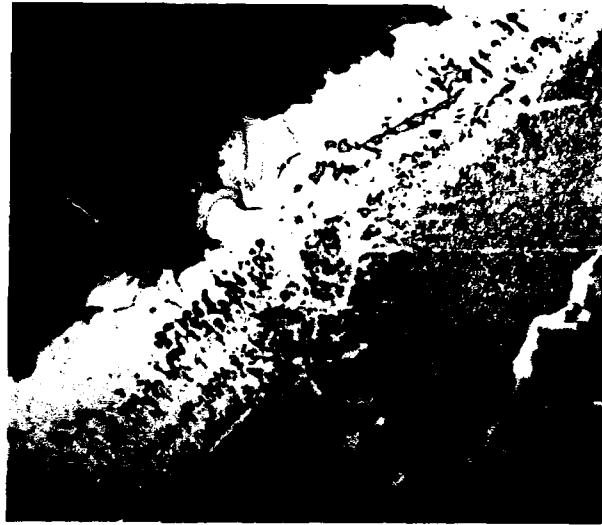

**Figure 10:** Optical micrograph using etchant (3). The darker phase at the outer edge of the coating is probably  $\gamma'$  formed by Al depletion. Grain-boundary carbides are also visible in the substrate.



**Figure 11:** Etchant (4);  $\beta$ ,  $\gamma$  and  $\gamma'$  phases have been preferentially attacked leaving carbide phases and interdiffusion zone precipitates. Note the plate-like appearance of precipitates projecting into the substrate (RHS).




**Figure 12:** Etchant (4) used to reveal grain boundary carbides.  $\gamma'$  attack has left voids in the matrix and grain boundaries.




**Figure 13:** Optical micrograph showing coating and substrate etched with etchant (4) for 10 sec.

**Figure 14:** SEM micrographs of the outer surface of a turbine blade with NiAl removed by etchant 2;

- a) shows the scale (top 1/2), and the interdiffusion zone, (bottom 1/2), connected by coating grain boundaries.
- b) magnification of grain boundaries in a).
- c) three regions of the coating are revealed here, starting from the LHS bottom,
  - inner and outer interdiffusion zone bands
  - Ni rich region of the coating (smoother diagonal band).

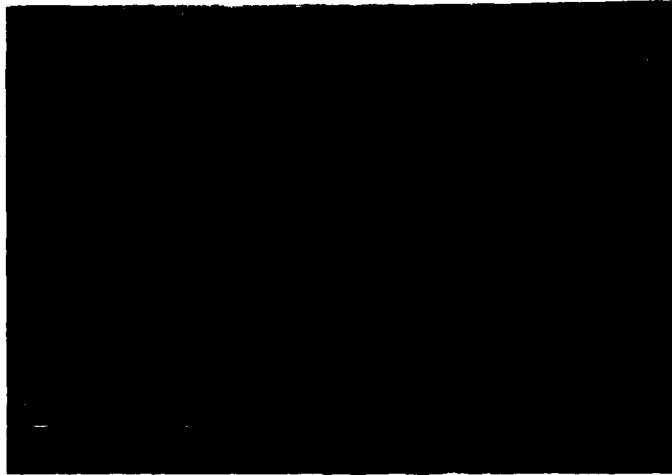

(a)

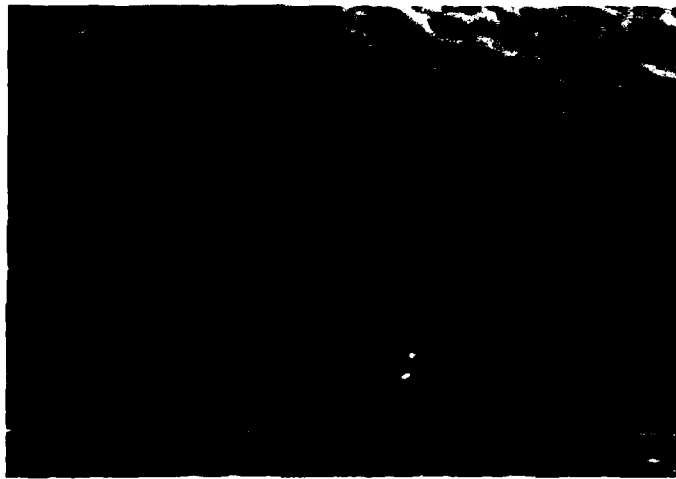

(b)



(c)



**Figure 15:** Optical micrograph showing the effects of carbide stain on superalloy IN738. Larger matrix carbides and smaller chain grain boundary carbides have stained brown ( $M_6C$ ).



**Figure 16:**  $M_{23}C_6$  carbides dispersed in superalloy René 80H.



**Figure 17:** Carbide stain used to delineate structure without etching. The micrograph reveals a fatigue crack running down a substrate grain boundary.



## DISTRIBUTION

### AUSTRALIA

#### Department of Defence

##### Defence Central

Chief Defence Scientist )  
AS, Science Corporate Management ) shared copy  
FAS Science Policy )  
Director, Departmental Publications  
Counsellor, Defence Science, London (Doc Data Sheet Only)  
Counsellor, Defence Science, Washington (Doc Data Sheet Only)  
Scientific Adviser, Defence Central  
OIC TRS, Defence Central Library  
Document Exchange Centre, DSTIC (8 copies)  
Defence Intelligence Organisation  
Librarian H Block, Victoria Barracks, Melbourne  
S.A. to Thailand MRD (Doc Data Sheet Only)  
S.A. to the DRC (Kuala Lumpur) (Doc Data Sheet Only)  
Director General - Army Development (NSO) (Doc Data Sheet Only)  
Defence Industry and Materiel Policy, FAS (Doc Data Sheet Only)

##### Aeronautical Research Laboratory

Director  
Library  
Chief, Aircraft Materials Division  
Divisional File, Aircraft Materials  
Author: P. Rohan  
N.E. Ryan

##### Materials Research Laboratory

Director/Library

##### Navy Office

Navy Scientific Adviser (3 copies Doc Data Sheet)  
Director of Aviation Systems Engineering - Navy  
Director of Naval Engineering Requirements - Aviation Systems  
Naval Support Command  
Superintendent, Naval Aircraft Logistics

##### Army Office

Scientific Adviser - Army (Doc Data Sheet only)

##### Air Force Office

Air Force Scientific Adviser  
Director General Engineering - Air Force  
AHQ (INT1)

Statutory and State Authorities and Industry

Aero-Space Technologies Australia, Systems Division Librarian  
Ansett Airlines of Australia, Library  
Australian Airlines, Library  
Qantas Airways Limited  
Civil Aviation Authority  
Hawker de Havilland Aust Pty Ltd, Victoria, Library  
Hawker de Havilland Aust Pty Ltd, Bankstown, Library  
Rolls Royce of Australia Pty Ltd, Manager  
BHP, Melbourne Research Laboratories

Universities and Colleges

Adelaide

Barr Smith Library

Melbourne

Engineering Library

Monash

Hargrave Library

Head, Materials Engineering

Newcastle

Library

Professor R. Telfer, Institute of Aviation

Sydney

Engineering Library

NSW

Physical Sciences Library

Library, Australian Defence Force Academy

RMIT

Library

Mr M.L. Scott, Aerospace Engineering

**NETHERLANDS**

National Aerospace Laboratory (NLR), Library

**NEW ZEALAND**

Defence Scientific Establishment, Library

**UNITED KINGDOM**

Defence Research Agency

Pyestock, Director

**UNITED STATES OF AMERICA**

Materials Information, American Society for Metals

The Chemical Abstracts Service

United Technologies Corporation, Library

**SPARES (10 COPIES)**

**TOTAL (63 COPIES)**

**DOCUMENT CONTROL DATA**PAGE CLASSIFICATION  
**UNCLASSIFIED**

PRIVACY MARKING

1a. AR NUMBER <b>AR-006-602</b>	1b. ESTABLISHMENT NUMBER <b>ARL-MAT-TM-404</b>	2. DOCUMENT DATE <b>MAY 1991</b>	3. TASK NUMBER <b>AIR 88/025</b>
4. TITLE <b>METALLOGRAPHY OF ALUMINIDE COATINGS</b>		5. SECURITY CLASSIFICATION (PLACE APPROPRIATE CLASSIFICATION IN BOXES) (E. SECRET (S), CONF. (C) RESTRICTED (R), UNCLASSIFIED (U)).  <div style="display: flex; justify-content: space-around;"> <div style="border: 1px solid black; padding: 2px; text-align: center;">U DOCUMENT</div> <div style="border: 1px solid black; padding: 2px; text-align: center;">U TITLE</div> <div style="border: 1px solid black; padding: 2px; text-align: center;">U ABSTRACT</div> </div>	6. NO. PAGES <b>22</b>  7. NO. REFS. <b>7</b>
8. AUTHOR(S) <b>P. ROHAN</b>		9. DOWNGRADING/DELIMITING INSTRUCTIONS  <b>Not applicable</b>	
10. CORPORATE AUTHOR AND ADDRESS <b>AERONAUTICAL RESEARCH LABORATORY 506 LORMER STREET FISHERMENS BEND VIC 3207</b>		11. OFFICE/POSITION RESPONSIBLE FOR: SPONSOR <b>RAAF</b> SECURITY <b>-</b> DOWNGRADING <b>-</b> APPROVAL <b>CAMD</b>	
12. SECONDARY DISTRIBUTION (OF THIS DOCUMENT)  <b>Approved for public release</b>  OVERSEAS ENQUIRIES OUTSIDE STATED LIMITATIONS SHOULD BE REFERRED THROUGH DETIC, ADMINISTRATIVE SERVICES BRANCH, DEPARTMENT OF DEFENCE, ANZAC PARK WEST OFFICES, ACT 2601			
13a. THIS DOCUMENT MAY BE ANNOUNCED IN CATALOGUES AND AWARENESS SERVICES AVAILABLE TO . . .  <b>No limitations</b>			
13b. CITATION FOR OTHER PURPOSES (E. CASUAL ANNOUNCEMENT) MAY BE <div style="display: flex; justify-content: space-around; align-items: center;"> <input checked="checked" type="checkbox"/> UNRESTRICTED OR         <input type="checkbox"/> AS FOR 13a.       </div>			
14. DESCRIPTORS <b>Protective coatings Gas turbine blades Metallography</b>		15. DISCAT SUBJECT <b>Nickle coatings Nickle alloys Etchants</b>	CATEGORIES <b>1103 2105 1106</b>
16. ABSTRACT  <i>Metallographic techniques have been established for the examination of gas turbine blades and their protective coatings. Particular attention was given to edge retention of specimens during polishing and to etchant selection to allow microstructural evaluation of major phases. Edge retention was achieved firstly by depositing a nickel plate over the specimen (by electroless deposition) and secondly, by minimizing the use of cloth polishing pads. Etchants were then evaluated for phase delineation in polished Allison T-56 turbine blades, (IN738 substrate alloy coated with high-activity nickel aluminide). Characteristics of four most useful etchants are described.</i>			

PAGE CLASSIFICATION  
**UNCLASSIFIED**

PRIVACY MARKING

THIS PAGE IS TO BE USED TO RECORD INFORMATION WHICH IS REQUIRED BY THE ESTABLISHMENT FOR ITS OWN USE BUT WHICH WILL NOT BE ADDED TO THE DISIS DATA UNLESS SPECIFICALLY REQUESTED.

16. ABSTRACT (CONT).

17. IMPRINT

**AERONAUTICAL RESEARCH LABORATORY, MELBOURNE**

18. DOCUMENT SERIES AND NUMBER

Aircraft Materials Technical  
Memorandum 404

19. COST CODE

333 010

20. TYPE OF REPORT AND PERIOD COVERED

21. COMPUTER PROGRAMS USED

22. ESTABLISHMENT FILE REF.(S)

23. ADDITIONAL INFORMATION (AS REQUIRED)